

3 SEPTEMBER 2009

As published in
Powder Injection Moulding International
www.pim-international.com

METAL, CERAMIC AND CARBIDE INJECTION MOULDING INDUSTRIES

POWDER INJECTION MOULDING

INTERNATIONAL



in this issue

Ceramic injection moulding
Post-sintering & finishing operations
Opportunities for MIM magnets

Ceramic injection moulding: a review of developments in production technology, materials and applications

Ceramic injection moulding (CIM) is a well established process for the mass production of complex shaped ceramic components. In the following review Dr. Tassilo Moritz and Dr. Reinhard Lenk from the Fraunhofer Institute for Ceramic Technologies and Systems (IKTS), Dresden, show how process and material developments have opened up a new world of possibilities for CIM, from micro parts to automotive, electronics and engineering solutions.

In July 1938 a method for making a refractory body was patented by the US patent office. Karl Schwartzwalder claimed in his patent a "method of making ceramic articles which consists in preparing a mixture of finely ground non-plastic ceramic material, and a resinous binder, forming a body from there by application of pressure, reforming said body by application of pressure and heat in sufficient degree to make the binder to flow thereby distributing the forming pressure throughout the body, permitting the body to harden and firing the hardened body to expel the binder and cause the non-plastic material to sinter together" [1].

Independently from this, in November 1940, Klinger et al. obtained a German patent claiming a method of producing spark plugs by injecting a ceramic compound with the addition of organic binders into a mould by application of pressure [2]. Thus, 70 years ago, ceramic injection moulding (CIM) was born – a shaping method which still today is the most efficient processing route for the high volume production of ceramic components with complex geometry.

During the first thirty years, however, ceramic injection moulding was of minor interest to the wider ceramics industry [3]. The progression into financial viability was based on

research and development efforts undertaken during the 1970's and 1980's [4]. Only in the 1970's did growing concern over energy, environment and natural resources increase interest in heat engines and national and international attention was focussed on the potential application of ceramics. Injection moulding provided a cost-effective fabrication method suitable for the mass production of the parts of a heat engine whose complex shape caused fabrication problems [5].

In 1984 Carborundum reported [6] considerable progress towards manufacturing developments, focusing much of its energy and resources on the injection moulding of turbocharger rotors. Injection moulding had enabled the company to produce such components as axial turbine blades and pre-combustion chambers. On a large scale, production included 8-inch-diameter turbine wheels for General Motors turbine engine and large static components for the automotive gas

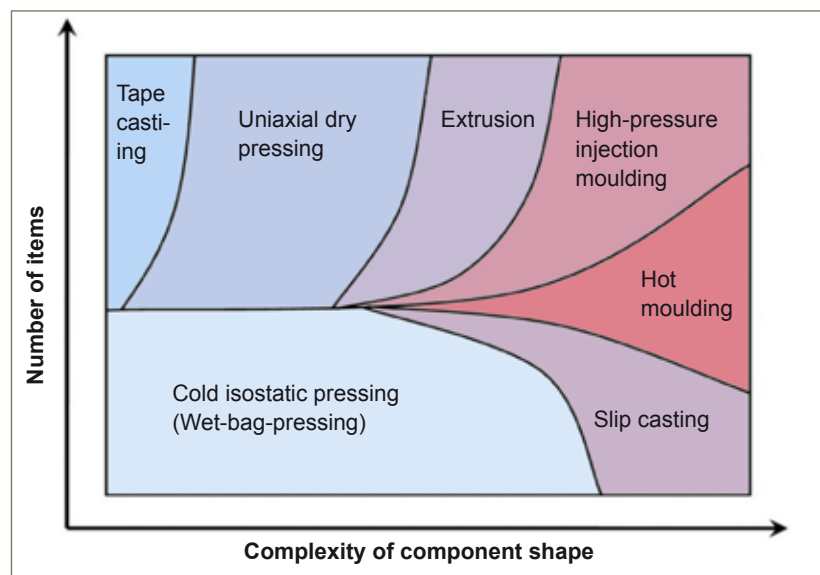


Fig. 1 Application areas of different ceramic shaping technologies in dependence on the lot size and the complexity of components geometry [16]

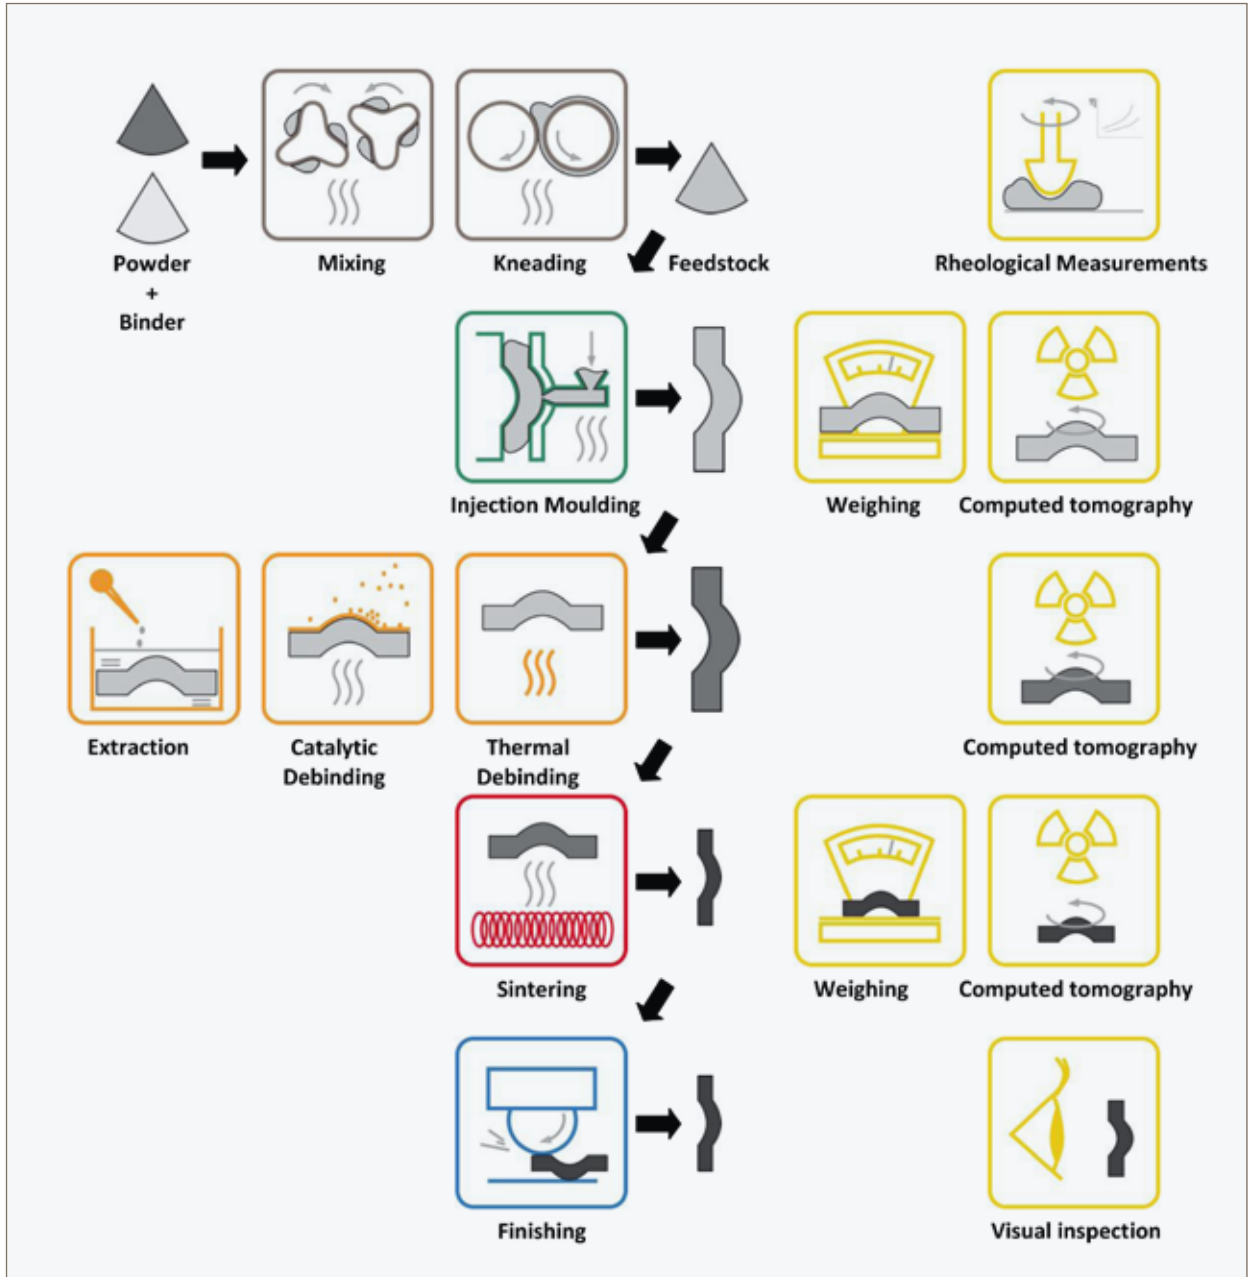


Fig. 2 Schematic view of the processing chain for ceramic injection moulding

turbine programmes.

Today around 330 companies from all over the world practice variants of powder injection moulding (PIM). Over 70% of these companies practice metal injection moulding (MIM), with a further 5% of companies producing a mixture of metals, ceramic and carbide components [7]. The remaining 25% practice CIM. Between 2006 and 2007 global annual sales growth in PIM was near 13% [7]. In comparison to MIM, ceramic injection moulding tends to produce larger and more highly priced components.

The market for advanced ceramic products is continuously growing

thanks to the unique property profile offered by ceramic materials. Ceramics are the material of choice for components that operate under extreme conditions, e.g. high temperatures, corrosive atmospheres, abrasive conditions or high loads at high temperatures. Moreover, ceramics combine excellent mechanical properties with low specific weight. This combination makes them interesting as light weight construction materials for moving components in automotive, aeronautic or space applications and for engine components.

Beside so-called structural ceramics, another very important

segment is electronic ceramics, including dielectrics, insulators, substrates, piezoelectric ceramics, superconductors and magnets. The latter forms the largest share of advanced ceramics [8].

Classification and process variants

Fig. 1 shows the most efficient application areas of different ceramic shaping technologies, dependent on the number of pieces which must be produced and the desired complexity of the component geometry. Unlike other powder shaping techniques, ceramic

injection moulding offers a relatively quick and cost effective route towards the mass production of geometrically complex, net-shape components with tight tolerances [9-14].

Injection moulding additionally offers the advantage of accomplishing ceramic parts with internal or external gears, undercuts, hollows, cross holes and serrations without any subsequent time and cost consuming mechanical operations [15].

In contrast to the raw materials used for traditional ceramics, which contain clay minerals and therefore showing a pseudoplastic behaviour, the powders for advanced ceramic products are synthetic high purity materials with no "plastic shaping" ability. For this reason, the powders must be combined with organic additives to give them the desired plasticity. According to the type of organic additive, the resulting powder-binder-mixtures, the feedstocks, are suited to one of two plastic shaping methods. These methods are 'low pressure' (LCIM) and 'high pressure' injection moulding, according to the viscosity of the feedstock and the resulting injection pressure.

Applied injection pressures between 0.2 and 5 MPa are counted as the low pressure area of the injection moulding process. Low pressure injection moulding primarily uses paraffin wax based binder systems [17- 20]. The advantages of low-pressure injection moulding relative to high-pressure CIM are:

- it is a simple and lower cost process
- with low pressure CIM there is less wear on the machine parts in contact with the powder batch, resulting in less contamination of the ceramic mix by metallic tooling
- it is easier to control the flow behaviour of the batch in LCIM
- the use of LCIM eliminates the separate mixing, pelletising and granulation steps necessary in high pressure injection moulding [18, 21].

Several disadvantages limit the use of this processing technology. In particular, defects which may remain in the moulded parts after sintering. A catalogue of the defects arising from different steps of production has been reviewed by Zhang et al. [22].

The processing cycle

High pressure CIM is in principle borrowed from the plastic injection moulding industry. It can be automated easily and is, unlike other ceramic shaping techniques, suited to high volume production. A schematic view of the processing chain of CIM is given in Fig. 2.

As with all other powder technological processing routes, the choice of the ceramic powder plays a dominant role in ceramic injection moulding. Specific surface area, particle size, size distribution, particle shape and the purity of the powder influence the properties of the injection moulding mass, the so-called feedstock, impacting on the sintering behaviour and the final properties of the ceramic component. Slight changes in particle shape, size distribution or the humidity of the air may influence the rheological behaviour of the feedstock [23].

Typical particle sizes in ceramic injection moulding are 1-2 μm [24], however the use of much finer particles down



Sunrock Ceramics
Industrial High-Temperature Solutions

2625 S. 21st Ave Broadview, IL 60155 (708) 344-7600

Sunrock Ceramics specializes in high alumina industrial ceramics for the most severe applications of the powder metallurgy and technical ceramics markets.

Broad offering focused on the unique demands of the PM and MIM industries

- Pusher plates for rapid cycle hydrogen atmosphere pusher furnaces
- Setter tiles and other sintering media
 - High purity to eliminate contamination
 - Pressed parts – very thin profiles available
- Wide assortment of press tooling available
- More complex kiln furniture shapes can be cast

Serving worldwide PM markets with fast turnaround

- Products presently in service in Europe, Asia & U.S.
- Fast leadtimes reduce in-house stocking

Contact us today to learn more.

USA: 001 708 344 7600

E-mail: dthurman@sunrockceramics.com.



www.SunrockCeramics.com



Fig. 3 Nozzle body for cooling systems of power stations with hot moulding tool (Courtesy MicroCeram GmbH)



Fig. 4 Advanced ceramic components made by micro-injection moulding (Courtesy Rauschert Heinersdorf-Pressig GmbH)

to submicron or nano region have been reported [25, 26]. Besides the average particle size, the width of the particle size distribution is important. According to German [27] very wide or very narrow size distributions prove easier to mould.

The feedstock for use in an injection moulding machine is a homogeneous compound of ceramic powder and a thermoplastic binder [9]. The first stage in the fabrication route requires the use of a binder system which will give suitable rheological properties to the ceramic to ensure mouldability [28].

There is considerable interest

in employing formulations with the maximum volume fraction of powder in order to achieve high green density and to reduce shrinkage on subsequent sintering. Volume loadings of 50 to 70% are desirable. Nevertheless, viscosity increases considerably with increases in filler loading and therefore it is necessary to reduce the viscosity as far as possible by adding plasticisers.

In injection moulding, mixing is a major factor for achieving a homogeneous powder-binder mix that is free from agglomerates, has optimum ceramic/binder content and still maintains sufficient fluidity for moulding

[3, 23, 29]. During mixing the powder particles are coated with dispersants to reduce the surface tension and, after that, integrate with the binder. Avoiding the formation of agglomerates is essential for two reasons:

- ceramic agglomerates function as minute porous sponges that trap the binder
- agglomerates function as defect points in the final sintered components, thereby reducing product strengths and reliability [30].

The mixing or compounding process is carried out in either batch mixers, such as sigma-blade mixers, or in continuous mixers, such as single [3] and twin screw extruders [24, 31] or shear roller compactors [9, 23, 32], at temperatures above the melting points of the binder components. Twin screw extruders and shear rollers offer higher shear rates than the batch mixers and therefore give better dispersion of the powder in the binder, but they can cause degradation of some of the binder components. Upon exiting the compounding device, the mixture is pelletised or granulated ready for delivery to the injection moulding machine.

Rheological data taken during moulding is important in assuring homogeneous mixing [27, 33]. Torque rheometry has proven best for assessing the critical solids loadings in designing feedstock systems. However, a capillary rheometry is required to determine shear rate and temperature dependent viscosity profiles. Such data is essential for successful computer simulation of the mould filling process.

Capillary rheometry is the most accurate measuring method of mixture homogeneity. Another method for characterising the flowability of a ceramic feedstock is the measurement of the melt flow index (MFI). Here, feedstock is molten at a certain temperature in a cylindrical mould and forced through a nozzle with a defined pressure. This determines the volume passing the nozzle within 10 minutes [34].

Binder systems and debinding concepts

According to Chartier et al. [35] four types of organic additives are needed to manufacture parts by injection moulding: binders, plasticisers, dispersants and lubricants. Binders give the necessary rheological behaviour to the

feedstock for injection moulding and the cohesion to the green part. Plasticisers lower the viscosity of the binder to fit it to the process used, while dispersants improve the state of dispersion of the powder in the organic phase and prevent the formation of agglomerates.

Finally, lubricants reduce wear between the feedstock and the tools. Polymers commonly chosen for high-pressure injection moulding are polypropylene [28], low density polyethylene [28], ethylene vinyl acetate [28], polystyrene [28], polymethyl methacrylate [36], polyvinyl butyral [36], or polyacetal [36]. As a processing aid, stearic acid is often applied [28].

BASF has developed a binder system which shows outstanding performance in terms of extremely short debinding times via catalytic debinding approaches and also demonstrates excellent shape retention during both debinding phases [10, 37]. The acetal is decomposed into formaldehyde in a catalytic debinding cycle which is controlled by the use of concentrated nitric or oxalic acid. The formaldehyde is then burned off in a two stage burner to keep nitric oxides and formaldehyde exhaust to a minimum [10, 36, 38].

Binders based on ceramic precursors including silanes, carbosilanes, siloxanes and silacanes have also been reported [38, 39]. Such binder systems lead to very low sintering shrinkage. During pyrolysis the ceramic precursors are converted into amorphous silicon nitride, silicon carbide or mixtures thereof. For preventing the formation of cracks, the pyrolysis must be carried out very slowly under a protective atmosphere.

Several publications report feedstock systems based on carrageenan [40], cellulose derivatives [41] or agar and water [31, 41-44]. Agar is a very widespread group of thermogelling polysaccharides. The water sublimates after the component has been moulded in a drying cycle, and the components are prepared for the final thermal debinding and sintering cycles. Critical issues for this system include the need of careful control of the feedstock's environment, as the contents of water determines the flow behaviour and solids loading. The injection moulded components show a gel type of behaviour and are flexible or rubbery until they have been dried [36]. This type of binder is only used for low pressure injection moulding.

In recent years, microwave drying has frequently been used; the other alternative is freeze-drying [45, 46]. Further alternative binder concepts which should be mentioned are: (1) freeze-casting, where the aqueous injection moulded feedstock is frozen in the mould cavity [47]; (2) hydrolysis assisted shaping of AlN by temperature induced hydrolysis [48] or (3) temperature-inverse injection moulding [49]. In the last mentioned method a cold aqueous feedstock is injected in the pre-heated mould of 80°C. Owing to a temperature induced reaction the binder strengthens and the green component can be ejected.

Beside the above mentioned catalytic debinding, in the case of polyacetal binder systems and the simple drying of components based on agar and water, thermal debinding is widely used to remove organics before sintering [14, 30, 38, 43, 50, 51]. Since thermal debinding takes place in the whole volume of the injection moulded component and decomposition products must leave the bulk by diffusion, the heating process has to be carried out very slowly to prevent the build up of internal pressures which can cause cracks and voids in parts. In most cases, a mixture of waxes

eMBe

PRODUCTS & SERVICE GMBH

learn how to control the powder's motion with eMBe

At eMBe, we have the products and services to help you "shape up" your metal or ceramic powder.

Develop your products with us by using our lab and our experience in additives design for sintering materials.

eMBe is a leading additive supplier for the ceramic and powder metal industry in Europe. Our services focus on product development and product innovation to continuously meet our customers' evolving needs.

Find our products applicable for

Ceramic Injection Moulding
Embemould® C and Licomont® EK 583

Compaction of metal powders
Embelube®

Metal Injection Moulding
standard and custom-made
Embemould® Metal Feedstocks

Embemould and Embelube are registered trademarks of eMBe
Licomont EK 583 is a registered trademark of Clariant



To learn more, please contact us:

eMBe Products & Service GmbH
Gemeindewald 7
86672 Thierhaupten, Germany
tel.: +49 8271 421988-3
fax: +49 8271 421988-4
servicepoint@embe-products.com
www.embe-products.com

LÖMI®

Quality
Innovativity
Service

Injection Moulding Debinding Furnaces

Exhibiting at
Euro PM2009
booth #39

- for metal and ceramic feedstock
- 50 to 2,500 litres
- extraction of binder by organic solvent or water
- combined or two-unit-systems
- including solvent recovery
- including vacuum drying
- technically mature and robust



LÖMI – excellence in solvent recycling, MIM debinding and explosion-proof systems since 1991

info@loemi.com
www.loemi.com



Fig. 5 Ceramic gear wheel in the green and sintered state made by two-component CIM combining alumina and zirconia toughened alumina (Courtesy Fraunhofer IKTS, designed by Robert Bosch GmbH)



Fig. 6 Thread stopper (Courtesy Fraunhofer IKTS, designed by Rauschert Heinersdorf-Pressig GmbH)

and polyolefins with various softening points is used in order to prevent the deformation of components during debinding.

The thermal decomposition of individual binder components takes place one after the other, slowly opening pores and allowing for the removal of subsequent decomposition

component, such as polyethylene glycol, and one insoluble. Debinding takes place in two steps. In the first step, the injection moulded components are placed in water to remove the soluble component of the binder. At the same time, a system of pore channels develops which allows a relatively fast removal

'To date, there has been no single debinding method that allows manufacturers to take full advantage of CIM's vast potential'

products. Binder components with higher decomposition points are called backbone polymers, maintaining the mechanical stability of the injection moulded part during the debinding process. To prevent deformation of the part occurring when the binder softens, the components can be embedded in a powder bed serving as a wicking media, or they can be placed on special sintering substrates.

In order to overcome the problems associated with thermal debinding, solvent debinding [52, 53] has been widely adopted by industry. In the solvent debinding process, a portion of the binder can be chemically removed by using solvents like acetone, trichloroethane or heptane. The large amount of open porosity after solvent debinding allows the degraded products to easily diffuse to the surface [43].

A more environmental friendly method is given by binder compositions containing one water-soluble

of the remaining component. Then the part is heated in a furnace to remove the insoluble component by thermal decomposition [38]. Solvent debinding has proven most successful in combining dimensional uniformity with reduced process times [27].

As a further alternative technique for debinding, extraction of organic binders by supercritical fluids has been investigated [54]. Carbon dioxide is currently the most popular fluid used due to its low cost and its convenient critical temperature of 31.1°C and critical pressure of 7.39 MPa [55].

Despite the variety of debinding mechanisms available, the debinding step is the limiting factor in CIM processing. To date, there has been no single debinding method that allows manufacturers to take full advantage of CIM's vast potential [30], because this processing step is the most time-consuming [56].

Injection moulding process: parameters, defects, proofing

The equipment used for injection moulding CIM parts is the same as the equipment that is used in the plastic injection moulding industry, with small modifications to reduce wear (hardened screw and barrel) and assure homogeneity (modification of screw design) during plastification [24].

In principle, high-pressure ceramic injection moulding can be carried out with two types of injection moulding machines – screw machines and plunger machines. The screw machine differs from the plunger type with respect to material conveying and plasticising [3]. In a screw machine, a major portion of heat comes from the frictional forces between screw material and cylinder, whereas a plunger machine heats the materials by conduction and convection only. Furthermore, in a plunger machine the pressure loss in the cylinder could be significant, and the pressure at the end of the plunger is much higher than the pressure at the nozzle.

To injection mould a ceramic part, the granulated feedstock is fed into the barrel of the machine and heated to produce a semi-fluid mass. The moulding medium is then forced into the mould cavity through a gated runner system. In screw machines a check-ring mechanism allows the auger to act as a piston, driving the material into the mould [31]. Typically, polymer and wax-based moulding compounds are heated in the moulding machine to temperatures of 130 – 200°C and are injected using barrel pressures between 50 and 150MPa.

Defects which result from the injection moulding process are irreversible and impair the quality of the finished ceramic components. A catalogue of the most frequent defects which may arise during ceramic injection moulding has been compiled by Zhang et al. [22]. Moreover, a comprehensive overview of injection moulding errors, their sources and helpful counteractions has been compiled [13].

Green parts that at first appear to be of good quality can possess internal stresses, which may in turn lead to cracks during later processing steps such as debinding. Local shrinkage differences should therefore be avoided. For this purpose, the use of a hot runner system has been proved to be promising [57]. Material cannot only be saved by hot runner systems, but also the manufacture of parts with fewer internal stresses can be achieved [58].

Because of the abrasive properties of the ceramic powders, the choice of a suitable hardened steel plays an important role for tool construction. For tool design, the geometry of a component and the production volume are crucial aspects. They affect the position of the component in the tool and the number of cavities, the design of the runner system, the type and the position of the sprue, the operating mode and the removal of the injection moulded parts (manually or automated) such as the ejection system (mould parting surface, slides, core pullers) [59].

Depending on the material, the powder packing density achieved by the solid volume content of the feedstocks, the powder particle size, shape and size distribution, the moulded ceramic green parts are typically 14-22 % larger (linear) than the sintered components owing to the shrinkage during sintering. This property of ceramic injection moulding has to be taken into consideration as an oversize factor for tool construction.

Quality control of ceramic components in the green, debound and sintered state is commonly carried out by weighing and by visual inspection. Combining both simple methods allows for the detection of surface cracks, impurities, pores, voids, distortions, incomplete parts or sink marks.

Measuring the density of the ceramic components after sintering is another indispensable method for characterising the performance of the injection moulded part, because most of the defects introduced in the green body during injection moulding either increase or even become obvious after sintering.

A more precise method for detecting deviations from the desired geometry or distortion of components is the 3D coordinate measuring process [26]. For detecting defects inside components already in the green state computed tomography [26, 60] is the non-destructive method of choice. Through computed tomography it is possible to detect entrapped air, voids, cracks, pores, inclusions, impurities, as well as weld lines, powder-binder-separations and density inhomogeneities [61] at an early stage.

MicroCIM

Besides the distinction between high pressure and low pressure ceramic injection moulding, a number of variations have been derived from the ceramic injection moulding process. One method – named after the size of the injection moulded parts – is micro ceramic injection moulding (MicroCIM).

MicroCIM can be carried out using either the high



HAMiLab-V1500

- The latest and most sophisticated microwave laboratory furnace
- Full instrumentation, including an optical pyrometer, with PLC controller
- Includes capabilities for low vacuum and process atmospheres
- Maximum temperatures up to 1600 Centigrade

Spheric Technologies, Inc.


4708 East Van Buren Street • Phoenix, AZ 85008
(602) 218 – 9292
Spherictech.com
info@spherictech.com



is the research subsidiary of the University of Applied Sciences Wiener Neustadt, Austria. As interface between industry, science and education we are pioneer in the field of powder injection moulding.

Services:

- Feasibility studies
- PIM part design (aided by simulation)
- PIM mould design (aided by simulation)
- PIM production of prototypes
- PIM pilot production
- PIM small series production
- PIM technology transfer



Example:

X-COOL CPU heat sink

based on 96 tubes (height: 30 mm, wall thickness 0.3 mm) made of pure copper; usage with various cooling medium and conventional high speed fans.

fo tec Forschungs- und Technologietransfer GmbH

Viktor Kaplan-Strasse 2
2700 Wiener Neustadt, Austria
Tel. +43/2622/90333-0
Fax +43/2622/90333-99
E-mail: office@fofec.at

www.fofec.at

Type of component	Ceramic material	References
• Engine components / Engineering		
Water pump seals	SiC	[90]
Nozzles, guides, gear wheels, screw threads Stators Precision dispensation nozzles Sensor covers Tooth belt wheel Sensor tubes Bearings Seals Scissors Micro electrodes for ultrasonic welding Drill bits	Si ₃ N ₄ Al ₂ O ₃ Al ₂ O ₃ Al ₂ O ₃ Mg-stabilized ZrO ₂ Al ₂ O ₃	[69] [31] [66] [66] [91] [19] [14] [14] [14] [20] [24]
• Textile industry		
Wire guides Textile thread guides Twist stopper	Al ₂ O ₃ Al ₂ O ₃ , SiC ZrO ₂ /Stainless steel	[66, 14] [66, 18, 92] [84]
• Medical/Dental applications		
Orthodontic brackets Dental implants Prosthetic replacements Abutments Endoscopic tools Tweezers	Al ₂ O ₃ Al ₂ O ₃ Al ₂ O ₃	[66, 69] [66] [93] [69] [69] [10]
• Watches/Jewelry		
Precision watch gears Watchcases	Al ₂ O ₃ ZrO ₂	[66] [14]
• Communication		
Ferrules Optical sleeves Soft magnetic components	ZrO ₂ ZrO ₂ Mn-Zn ferrite	[94, 9] [94, 95] [96]
• Exhaust system components		
Oxygen sensor components	ZrO ₂	[90, 31]
• Metallurgy		
Ceramic casting cores	Al ₂ O ₃ /ZrO ₂ SiO ₂	[97, 24]
• Automotive components		
Valve components Turbocharger rotors Swirl chambers for high power turbocharged diesel engines Radial rotors with integrated ceramic shaft Airbag components Glow plug for diesel engines Gear wheel for fuel pumps	Al ₂ O ₃ , Si ₃ N ₄ SiC Si ₃ N ₄ SiC Si ₃ N ₄ + MoSi ₂ Al ₂ O ₃ / zirconia toughened alumina (ZTA)	[15, 98] [6] [99] [100] [24] [60]
Valve seat Components used on the BMW7 series automatic gear lever	Si ₃ N ₄ /SiAlON ZrO ₂ (black)	[60] [107]
• Electrical components		
Electrical components for automotive exhaust RF and electrical insulators Microwave dielectric components Electrical micro heater Cooling socket for electronic components Heat sinks, electronic packages	Al ₂ O ₃ , steatite Al ₂ O ₃ Ba(Zn _{1/3} Ta _{2/3})O ₃ Al ₂ O ₃ /TiN AlN	[101] [66] [102] [80] [92], [24]
• Home appliance and office equipment		
Injector for percolators Cups Printer head, disc drive rocker arm, camera components, micro gears in electrical toothbrush Pepper mill grinding gears Inkjet printheads Back cover of mobile phones	ZrO ₂ Porcelains Al ₂ O ₃ Al ₂ O ₃ ZrO ₂ (black)	[103] [42] [24] [104] [105] [37, 107]

pressure [62, 63] or low pressure methods [20, 64, 65] depending on the binder system. Intricate components with 18µm features, including through holes, gear teeth and screw threads are well suited for MicroCIM production. MicroCIM parts weighing as little as 0.0004g serve in a wide variety of applications where high temperatures and caustic environments preclude most metals and engineered thermoplastics [66]. Micro related products can be used in the fields of information and communication technology, medical and biotechnology, such as micro-sensor and micro-actor technology [67].

MicroCIM allows the manufacturing of precision products characterised by minimal wall thicknesses of 20µm, aspect ratios up to 20 or structural details in the range of 50µm or in certain cases less than 20µm, with a surface roughness of about $R_z < 0.05\mu\text{m}$ [68- 71].

Good examples of micro injection moulded devices are multi fibre connectors with 16 multi-mode channels, or containers for 3D cell culture systems using micromechanically cut mould inserts. For the adaption of the process to micro manufacturing, however, additional features had to be developed and implemented. Although there is a relatively wide range of materials available for CIM, it is necessary to focus on powders of small particle size. The initial powder requirements for MicroCIM are more stringent than that for conventional CIM. The powder must be homogeneous; and the grain size of the sintered part should be at least about one order of magnitude smaller than the minimum internal dimensions of the micro-component in order to obtain a reasonably isotropic behaviour [67, 72].

With respect to the surface quality of the replicated structures, the best results have been achieved by using ceramic powders with a mean particle diameter of 0.5µm or even smaller. The demand to process finer powders, including even the utilisation of nano powders,



Fig. 7 Watch lunette (Courtesy BRÖLL GmbH)



Fig. 8 Electrically conductive CIM part made of TiO_2 , embedded in an injection-moulded plastic assembly (Courtesy Kläger Spritzguss GmbH & Co. KG)

can therefore be regarded as one of the most important results of research carried out to-date in MicroCIM [73].

To obtain a viscosity of the plastic melt which is low enough to fill even the smallest structural details down to the submicrometer range, a so-called variotherm temperature conductor is used for heating the moulding tool near the melting point of the feedstock prior to its injection into the tool [73, 74]. Due to the high fragility of most microstructures, highly precise tool movements have to be assured in MicroCIM. To enable the injection process to be accelerated or slowed down in a controlled way by means of ramps, injection moulding machines with position regulated screws have been developed [63]. Moreover, micro components are considerably different to handle from macroscopic components, for instance in micro dimensions, electrostatic forces exceed the gravitational force so that micro parts sometimes stick to handling systems instead of dropping.

Alternatives to MicroCIM are rare. LIGA techniques are usually only suitable for 2D geometries, and most of the techniques are too expensive to become cost-effective in the near future [75]. Good examples of ceramic micro components are a cogwheel for micro motors which has been manufactured by means of a fully-automatic series production of CIM moulding process and a ferrule with a through hole diameter of $125\mu\text{m}$ [63].

To improve the precision and the accuracy of surface micro structures such as the homogeneity of injection moulded parts, the shaping process

can also be carried out as injection compression moulding. This means, after injecting the feedstock in the mould cavity the tool is compressed by a stroke of 0.2 to 0.3mm providing an additional embossing step.

Multicomponent PIM

Micro components are not only becoming ever smaller, they are also often required to have several functions at one time [63]. Such a trend can also be seen for advanced ceramic macro components. The first ideas

manufacture and surface engineer a component in a single process has attractive implications, both technically and financially, particularly when large numbers of complex shaped components are to be produced [78].

Research results have shown that ceramic materials can be combined in one part by 2C-CIM [78- 80]. The following systems have been produced:

- a component with alumina skin and core, possessing a $0.5\mu\text{m}$ particle size skin layer surrounding a $1\mu\text{m}$ particulate core [78]

'the ability to manufacture and surface engineer a component in a single process has attractive implications, both technically and financially'

and patents concerning co-injection moulding of two synthetic materials appeared 40 years ago [76].

The first applications of two-colour injection moulding were keys with abrasion-resistant symbols for computer keyboards or telephones [77]. Applications from the automotive sector show that co-injection moulding is today applied to a great variety of automotive components. Thanks to this technique, not only different colours but also thermal, mechanical, electrical and optical properties of plastics can be combined in one processing step [77].

In the mid 1990's multi-component injection moulding was applied to PIM technology since the ability to

- toughened components with a skin containing 20 vol.-% partially stabilised zirconia surrounding a 100% alumina core [79]
- a ceramic heater consisting of different Al_2O_3/TiN -mixed ceramics [80].

The combination of different ceramic materials and ceramics with metals by two-component injection moulding has been further described [81]. By systematically combining ceramic and metal powder components via two-component injection moulding, new and highly functional composites with property combinations such as conductive/insulating, magnetic/non-magnetic, thermal conductive/thermal



Fig. 9 Thread guide (Courtesy BRÖLL GmbH)



Fig. 10 Cooling box for electrical components (Courtesy Fraunhofer IKTS)

insulating or ductile/hard are achievable [82].

All studies on 2C-CIM have confirmed that sintering rate control is crucial to the success of this shaping method. Both components must sinter at similar rates and at similar positions in the sintering temperature profile to avoid delaminations. The sintering behaviour can be altered by lowering the powder content of one mix, and hence its green density, at the risk of a porous component or by the addition of a second non-sintering composite phase [78]. The variety and combination of materials that can be used in the manufacture of metal or ceramic components by powder co-injection moulding is more limited due to the requirement for compatible sintering characteristics [78]. Depending on the design and size of the contact area of both ceramic materials the feedstock components can be injected simultaneously or sequentially. A quick succession of the injection processes is essential for a high compound strength [80].

In order to be successful in two-component powder injection moulding it is essential to develop feedstocks with comparable shrinkage rates during co-debinding and co-sintering of the injection moulded material compounds. The absolute shrinkage during sintering depends on the solid content of the feedstock, i.e. the green packing density of the powder. Furthermore, the shrinking behaviour of the powders are influenced by the type of ceramic powder used and its particle size distribution [60].

To achieve defect-free material compounds after the thermal treat-

ment it is necessary that the onset of shrinkage of both materials is comparable and that the thermal expansion coefficient of the ceramic materials is almost the same. The latter criterion is decisive during cooling of the material compound after sintering for preventing high cooling stresses. Moreover, a similar thermal expansion coefficient would be crucial for surviving cyclic heating and cooling of the compound during application [26].

The large-scale production of multifunctional components with complex geometries is also the goal of a further process variant – the so-called inmould labelling where ceramic injection moulding is applied to complete several inserts like ceramic or metallic green tapes [83, 84] or green components. Inmould-labelling combines shaping methods like tape casting with injection moulding and offers some additional process-relevant advantages:

- very thin functional layers can be realised
- intermediate layers improve the material composite and facilitate transitions in thermal expansion behaviour
- extremely high aspect ratios can be obtained within the composite

Stainless steel and yttrium-stabilized zirconia have been chosen as a material combination and has been successfully combined by inmould-labelling such as by two-component injection moulding [82 and 85].

Special process variants

A further important method of ceramic injection moulding is gas assisted injection moulding [86; 87]. Since the size of injection moulded parts is limited by economic efficiency due to the expensive powders needed, as well as the time required for the debinding of the parts with high wall thickness, the combination of CIM with gas-assisted injection moulding is of great importance.

Gas-assisted powder injection moulding (GAPIM) can be subdivided into two different processes, the full shot and the short shot process. Using the full shot process, the gas is injected when the cavity is filled completely with melt. The injected gas pressure forms a bubble in the inner core by pressing the melt into an additional cavity. In the short shot process the gas is injected into the partly filled cavity. The gas presses the melt to the end of the cavity. When processing ceramic feedstocks by GAPIM, time and costs can be saved in the debinding step. On the other hand, parts of high geometrical complexity used to pipe corrosive media under high pressure or temperature can be produced in an automated way. The use of GAPIM is described in literature for alumina and silicon nitride ceramics [87].

For continuous or semi-continuous production of ceramic parts, extrusion is very interesting because of the relative simplicity of the equipment. All type of plasticised material can be extruded by pressing them through the orifice of a die. Therefore, for thermoplastic extrusion of ceramic bodies, in principle the same polymer binders,

plasticisers, surfactants and sliding agents known for ceramic injection moulding can be used [88]. Typical products are thin walled-tubes [89], pipes, or fibers.

Summary and outlook

According to [106] major growth areas in PIM in the coming years can be seen in multi-component PIM and MicroPIM. Multi-component PIM enables several different materials to be combined in a single component, although the difficulties lie in the combination of the physical properties of the various materials.

In the case of MicroPIM the challenge is to develop a suitable feedstock and high-precision, miniaturised mould cavities. The fully automatic process for removing the micro components also represents an enormous technical challenge.

For industry, process optimisation and cost-reduction are of great concern. Universities and research centres efforts are focused on computer modelling of moulding, debinding and sintering. Computer simulation of the PIM process to predict size, shape, defects and to properly design tool and production operations is a major activity.

Another goal is the production of very small medical and computer devices using fine-grained powders [4].

Acknowledgements

This review article bases on input from the members of the Expert Group "Ceramic Injection Moulding (CIM) in the German Ceramic Society (DKG).

Contact

Dr. Tassilo Moritz, Dr. Reinhard Lenk
Fraunhofer-Institut für Keramische
Technologien und Systeme, IKTS
Winterbergstraße 28,
01277 Dresden, Germany
Tel: +49 351 2553 747
Fax: +49 351 2554 197
Email: tassilo.moritz@ikts.fraunhofer.de

References

- [1] K. Schwartzwalder: Refractory Body and Method of Making same, US-Patent 2,122,960
- [2] E. Klingler et al.: Verfahren und Vorrichtung zur Herstellung von Zündkerzensteinen, Deutsches Patent 699080
- [3] B. C. Mutsuddy: Equipment selection for injection moulding, *Ceram. Bull.* 68(1989), 10, 1796-1802
- [4] R. M. German: Global research and development in powder injection moulding, *Powder Injection Moulding International* 1(2007), 2, 33-36
- [5] B. C. Mutsuddy: Mechanical properties of injection molded ceramics, *Powder Metallurgy International* 19(1987), 2, 43-45
- [6] J. W. MacBeth: Ceramic Engine Components Reduce Wear, Friction, *Ceramic Industry* (1984), 7, 33-45
- [7] R. M. German: Divergences in global powder injection moulding; *Powder Injection Moulding International* 2(2008), 1, 45-49
- [8] Z. S. Rak: Advanced forming techniques in ceramics, *Klei Glas Keramiek* 22(2001), 4, 19-24
- [9] M. v. Witzleben et al.: Maßgeschneiderte Feedstocks für den keramischen Spritzgießprozess, *Keramische Zeitschrift* (2008), 5, 344-346
- [10] C. Borchard-Tuch: Keramik und Metalle durch Spritzguss in Form gebracht, *Chem. Unserer Zeit* 38(2004), 282-283
- [11] G. Bandhyopadhyay et al.: Effect of Powder Characteristics on Injection Moulding and Burnout Cracking, *Am. Ceram. Soc. Bull.* 73(1994), 3, 107-114
- [12] P. Suri et al.: Effect of mixing on the rheology and particle characteristics of tungsten-based powder injection molding feedstock, *Materials Science and Engineering A356* (2003), 337-34
- [13] M. Maetzig et al.: Strategies for injection moulding metals and ceramics. In: *Proceedings of the 2002 World congress on Powder Metallurgy & Particulate Materials*, June 16-21, Orlando, Florida, 10-33 - 10-41
- [14] H.-J. Sterzel: Spritzgießen keramischer Bauteile, *Mat.-wiss. u. Werkstofftech.* (1997), 28, 534-542
- [15] L. Deuber: Spritzgussverfahren für Hochleistungskeramiken, *Technika* (2003), 21, 20-22
- [16] R. Lenk: Heißgießen von Keramik. *Das Keramiker Jahrbuch* 2002. Göller-Verlag, Baden-Baden, 13-26
- [17] R. Lenk: Hot Moulding - An Interesting Forming Process, *cfi, Ber. Dtsch. Keram. Ges.*, 72(1995), 10, 636-642
- [18] C. Toy et al.: A new ceramic thread-guide composition via low-pressure injection molding, *J. Mat. Proc. Technol.* 51(1995), 211-222
- [19] H. S. Soykan et al.: Injection moulding of thin walled zirconia tubes for oxygen sensors, *Advances in Applied Ceramics* 104(2005), 6, 285-290
- [20] L. V. Sudnik et al.: Ceramic Composite Materials for MicroElectrodes produced by Injection Moulding, *Proc. of the 2nd European Symposium on Powder Injection Moulding*, Oct. 18-20, 2000, Munich, 253-257
- [21] S. Novak et al.: The effect of water on the behaviour of alumina-paraffin suspensions for low pressure injection moulding (LPIM), *J. Europ. Ceram. Soc.* 20(2000), 2175-2185
- [22] J. G. Zhang et al.: A catalogue of ceramic injection moulding defects and their causes, *Industrial Ceramics*, 9(1989), 2, 72-82
- [23] W. Kollenberg: Keramischer Spritzguss - Neue Aspekte für den Werkzeugbau, *Der Stahlformenbauer* 17(2000), 5, 110-114
- [24] P. J. Verpoort et al.: Overview of powder injection moulding, *Advanced performance materials*, 3(1996), 2, 121-151
- [25] F. Kern et al.: Thermoplastisches Spritzgießen von Nanokeramiken. *Stuttgarter Kunststoff-Kolloquium*, 20 * (2006) Seite 3/V2.1-8
- [26] A. Mannschätz et al.: Challenges in Two-Component Ceramic Injection Moulding, *cfi/Ber. DKG* 86(2009), 4, E25-E28
- [27] R. M. German et al.: Status of Powder Injection Molding for a Variety of Materials (Including Heat and Corrosion Resistant): I, *Industrial heating* 61(1994)5, 44-48
- [28] M. J. Edirisinghe et al.: Rheology of Ceramic Injection Moulding Formulations, *Br. Ceram. Trans. J.*, 86(1987), 18-22
- [29] M. Trunec et al.: Effect of powder treatment on injection moulded zirconia ceramics. *J. Eur. Ceram. Soc.* 20(2000), 859-866
- [30] G. Krug: New process solves CIM debinding dilemma, *Industrial Heating* 70(2003), 4, 35-39
- [31] C. Ballard: Ceramic injection moulding meets the demand for manufacturing complex shapes, *Ceramic Industry* 147(1997), 3, 42-44
- [32] A. Albers: Der Walzengranulator, eine neuartige Kompaktier- und Granuliermaschine, *Chem. Ing. Tech.* 78(2006), 12, 1871-1876
- [33] P. Quirnbach et al.: Nutzung der Spritzgießtechnologie innerhalb einer modernen Geschirrfertigung, *cfi/Ber. DKG* 81(2004), 1-2, D9-D13
- [34] J. Knothe: Keramische Bauteile - Gestaltungsfreiheit durch Spritzgießen, 17. IKV-Kolloquium, Aachen (1994), 382-389
- [35] T. Chartier et al.: Injection moulding of hollow silicon nitride parts using fusible alloy cores, *Ceramics International* 27(2001), 821-827
- [36] K. F. Hens et al.: Injection Molding of Various Metals and Ceramics using an Acetal Binder, *PM2TEC, Advances in Powder Metallurgy & Particulate Materials*, B 2(1995), 6.27-6.36
- [37] G. Schlieper: Feedstock for Powder Injection Moulding: production and commercial suppliers, *Powder Injection Moulding International*, 2(2008), 3, 23-32
- [38] G. H. Wroblewska: Structural ceramics with complex shape - forming methods, *Ceramic Engineering and Science Proceedings*, 22(2001), 3, 43-50
- [39] R. Schubert: Entwicklung von Verfahren zur Herstellung von Präzisionsformteilen aus polymerkeramischen Werkstoffen im Urformverfahren für Fahrzeug- und Maschinenbautechnik. Report-Nr. FKZ 03N3088B, bmbf. Bundesministerium für Bildung und Forschung, Forschungsberichte, (2004), 1-52
- [40] A. Millán et al.: Aqueous gel-forming of silicon nitride using carrageenans, *J. Am. Ceram. Soc.* 84(2001), 1 62-64
- [41] R. J. Huzzard et al.: A water-based system for ceramic injection moulding. *J. Eur. Ceram. Soc.* 17(1997), 211-216
- [42] I. Santacruz: Aqueous Injection Moulding of Porcelains, *Journal of the European Ceramic Society* 23 (2003), 2053-2060
- [43] W.-W. Yang et al.: Solvent debinding mechanism for alumina injection molded compacts with water-soluble binders, *Ceramics International* 29 (2003), 745-756
- [44] S. Olhero et al.: Feedstock formulations for direct consolidation of porcelains with polysaccharides, *J. Am. Ceram. Soc.* 84(2001), 4, 719-725
- [45] A. 1. Fanelli et al.: New Aqueous Injection Moulding Process for Ceramic Powders, *J. Am. Ceram. Soc.* 72(1989), 1833-1836
- [46] J. A. Mangels: Low-Pressure Injection Moulding, *Am. Ceram. Soc. Bull.* 73(1994), 5, 37-41
- [47] K. Araki et al.: New freeze casting technique for ceramics with sublimable vehicles, *J. Am. Ceram. Soc.* 87(2004), 10, 1859-1863
- [48] S. Novak et al.: Principles of the hydrolysis assisted solidification (HAS) process for forming ceramic bodies from aqueous suspension, *J. Eur. Ceram. Soc.* 22(2002), 289-295

- [49] D. Penner: Temperaturinverser siliciat-keramischer Spritzguss, cfi/Ber. DKG 82(2005), 8, D15-D19
- [50] M. S. Park et al.: Water-soluble binder of cellulose acetate butyrate/polyethylene glycol blend for powder injection molding, *J. Mat. Sci.* 36(2001), 5531 – 5536
- [51] M. Trunec et al.: Thermal Debinding of Injection Moulded Ceramics. *J. Eur. Ceram. Soc.* 17(1997), 203-209
- [52] K.P. Johnson: Process for fabricating parts from particulate material, US. Patent 4,765,950
- [53] R.E. Wiech, Jr.: Manufacture of parts from particulate material, US Patent 4,197,118
- [54] T. Chartier et al.: Supercritical debinding, *Ceramics Transactions* 51(1995), 327-331
- [55] S. Matthews et al.: The Manufacture of Porous Ceramics Using Supercritical Fluid Technology, *Advanced Engineering Materials* 10(2008), 3, 253-255
- [56] G. Himpel et al.: Optimisation of Thermal Debinding from Injection Moulded Ceramic Parts, cfi, Ber. Dtsch. Keram. Ges., 74(1997), 7, 368-371
- [57] W. Michaeli et al.: Ceramic injection moulding using a hot runner system. *Proceedings of the 4th Intl. ESAFORM Conf. on Material Forming*, April 23-25, 2001, Liège, Belgium, 93-96
- [58] W. Michaeli et al.: Hot runner molds aid powder injection molding, *Modern Plastics International* 5(1996), 75.
- [59] L. Merz et al.: In Form gebracht - spritzgegossene Keramikbauteile mit maßgeschneidertem Eigenschaftsprofil, *Pulvermetallurgie in Wissenschaft und Praxis*, 21(2003), 277-289
- [60] T. Moritz: Two-component CIM parts for he automotive and railway sectors, *Powder Injection Moulding International* 2(2008), 4, 38-39
- [61] D. Niedziela et al.: On numerical simulations of powder injection moulding, *Proceedings of the NAFEMS Seminar „Simulation of Complex Flows (CFD) – Applications and Trends*, March 16-17, 2009, Wiesbaden, Germany
- [62] V. Piotter et al.: Micro powder-injection moulding of metals and ceramics. *Sadhana* 28(2003), Parts 1&2, February/April 2003, 299-306
- [63] H. Walcher: PIM-Products: Small but effective! cfi/Ber. DKG 80(2003),11, E33-E36
- [64] R. Knitter et al.: Ceramics microfabrication by rapid prototyping process chains, *Sadhana* 28(2003), Parts 1&2, 307-318
- [65] B. Alm et al.: Formgebung von Mikrobauteilen und Mikrostrukturen aus Keramik, *Keramische Zeitschrift*, 52(2000), 4, 312-315
- [66] T. Ayers: Micromini ceramics sport supersized properties. *Machine Design*, 75(2003), 9, 59-62
- [67] Z. Y. Liu et al.: Micro-powder injection molding, *Journal of Materials Processing Technology* 127(2002), 165-168
- [68] V. Piotter et al.: Fabrication of micro-components by micromachining and injection moulding, *Proc. of 2nd Intern. Euspen Conf.*, May 27-31, 2001, Turin, Italy
- [69] M. Sutter: Mikrospritzgießen bringt Keramik in Hochform, *Mikroproduktion* (2009), 1, 48-51
- [70] F. Petzoldt: Micro powder injection moulding – challenges and opportunities, *Powder Injection Moulding International*, 2(2008), 1, 37-42
- [71] T. Moritz et al.: Modular Micro Reaction System Including Ceramic Components, *International Journal of Applied Ceramic Technology* 2(2005), 6, 521-528
- [72] W. Bauer et al.: Pulverspritzgießen von keramischen Mikrobauteilen, *Keramische Zeitschrift* (2004), 5, 292-297
- [73] V. Piotter et al.: Micro Powder Injection Moulding – Latest Developments. *PM2TEC, Advances in Powder Metallurgy & Particulate Materials*, (2008), 4/200-205
- [74] M. Maetzig et al.: Spritzgießmaschine und Werkzeugtechnik für das Pulverspritzgießen von Präzisionsbauteilen, *Mikrosystemtechnik Kongress*, (2005), 151-154
- [75] R. Zauner et al.: Micro powder injection molding for microstructured components. *Internationales Plansee Seminar*, 16(2005), 59-68
- [76] B. Rief: Mehr Farbe und Funktion. *Kunststoffe* 6(2003), 20-26.
- [77] G. Steinbichler: Multifunktionalität in einem Arbeitsschritt. *Kunststoffe – Synthetics* 42 (1995), 9, 44-52.
- [78] J. R. Alcock et al.: Surface engineering by co-injection moulding. *Surface and Coatings Technology* 105(1998), 65-71
- [79] S. Hanson: Surface engineering by powder coinjection moulding. *Surface Engineering* 15(1999), 2, 159-162
- [80] G. Finnah et al.: Drei Sonderverfahren in einem – 2K-Mikro-Pulverspritzgießen. *Kunststoffe* (2005), 1, 58-61
- [81] R. Lenk et al.: Formkörper aus einem Werkstoffverbund, Verfahren zu seiner Herstellung und Verwendung, Patentschrift DE 196 52 223 C2
- [82] A. Baumann et al.: Steel-Ceramic Compounds by Multi-Component Injection Moulding, *InterCeram* 56(2007), 6, 414-419
- [83] T. Moritz et al.: Keramischer und/oder pulvermetallurgischer Verbundformkörper und Verfahren zu ihrer Herstellung, Offenlegungsschrift DE 10 2007 003 192 A1
- [84] A. Baumann et al.: Developments in Multi-Component Powder Injection Moulding of Steel-Ceramic Compounds using Green Tapes for Inmould Label Process, *Powder Injection Moulding International*, 2(2008), 1, 55-58
- [85] A. Baumann et al.: Manufacturing of Ceramic-Metal Composites by Combining Tape Casting and Injection Molding. In: J. G. Heinrich and C. Aneziris, *Proc. 10th ECerS Conf.*, Göller Verlag, Baden-Baden, 2007, 413-416
- [86] W. Michaeli et al.: New opportunities by gas-assisted powder injection moulding (GAPIM). *European Symposium on Powder Injection Moulding*, 2, EuroPM, European Congress and Exhibition on Powder Metallurgy, (2000), 85-89
- [87] W. Michaeli et al.: New perspectives for ceramic injection molding with gas injection. *Advanced Engineering Materials* 2(2000) 12, 827-832
- [88] F. Clemens F et al.: Thin wall ceramic tubes by extrusion of thermoplastic ZrO₂ compounds. In: V. Kermel, V. Lardot, D. Libert, I. Urbain (Ed.), *Euro Ceramics VII*, Trans. Tech. Publications Ltd PT 1-3 206-2 (2002), 425-428
- [89] M. Trunec: Fabrication of zirconia- and ceria based thin wall tubes bey thermoplastic extrusion, *J. Eur. Ceram. Soc.*, 24(2004), 4, 645-651
- [90] D. Whittaker: Powder injection moulding looks to automotive applications for growth and stability, *Powder Injection Moulding International* 1(2007), 2, 14-22
- [91] T. Pfefferkorn et al.: Analyse des Keramikspritzgießprozesses für komplexe Bauteilgeometrien. *Keramische Zeitschrift* (2006), 4, 262-266
- [92] G. Himpel et al.: Spritzgegossene Aluminiumnitridkeramik für Anwendungen in der Elektronik, *Keramische Zeitschrift*, 49(1997), 10, 822-829
- [93] J. L. Johnson et al.: Processing of biocompatible materials via metal and ceramic injection molding. MPMD, *Materials and Processes for Medical Devices Conference*, (2004), 325-330
- [94] M. Beck et al.: PIM von Keramik-Ferrulen für Glasfaser-Verbindungen im Monomode-Bereich. Wissenschaftliche Berichte / Forschungszentrum Karlsruhe in der Helmholtz-Gemeinschaft, 7000 (2004), 19-34
- [95] S. I. Lin: Near-net-shape forming of zirconia optical sleeves by ceramics injection molding *Ceramics International* 27 (2001), 205-214
- [96] A. J. Pigram et al.: The production of Mn-Zn ferrite ceramics by ceramic injection moulding. *J. Mat. Sci.* 29(1994), 6420-6426
- [97] S. Uram: Injection molding of ceramic components provides flexibility in metal casting and forming. *Industrial Heating*, 54(1987), 4, 42-43
- [98] M. Pidria et al.: Near net shape, low cost ceramic valves for advanced engine applications *Materials Science Forum*, 426-432(2003), 3, 2321-2326
- [99] M. Murachi et al.: Injection-molded silicon nitride swirl chamber for high power turbo-charged diesel engines. *Ceramic Materials and Components for Engines*, DKG (1986), 4, 1181-1188
- [100] K. A. Schwetz et al.: Development of injection molded turbine components of aluminium-doped alpha silicon carbide. *Technical Ceramics, Proc. of the Final Contractors' Meeting* (1988) Nov, 75-82
- [101] B. A. Mathew: Powder Injection Molding Technology for Large Metal and Ceramic Components and Systems, *Advances in Powder Metallurgy and Particulate Materials* (2003), Part 8, 254-261
- [102] S. Liu et al.: Structural, chemical and dielectric properties of ceramic injection moulded BaZn_{1/3}Ta_{2/3}O₃ microwave dielectric ceramics, *J. Eur. Ceram. Soc.* 26(2006), 3273-3278
- [103] anonym: Die Zukunft formen. Spritzgießsystemlösungen. *SCOPE* (2007), 10, 36-38
- [104] M. v. Witzleben et al.: Keramisches Spritzgießen – auf den Feedstock kommt es an. *Konstruktion* (2007), 4, IW11-12
- [105] anonym: Ceramic inkjet printhead. *Powder Injection Moulding International* 2(2008), 4, 26
- [106] U. Haupt: Arburg sets the pace in the production of moulding machines for PIM. *Powder Injection Moulding International* 2(2008), 3, 49-52
- [107] B. Williams: Oechsler AG proves its competence in ceramic injection moulding with new BMW applications. *Powder Injection Moulding International* 3(2009), 2, 31-35

Subscribe today for only £95 and stay up-to-date with PIM industry developments



Subscribe to *Powder Injection Moulding International* today. Return by fax to: +44 (0)1743 469 909.

I would like to subscribe to *Powder Injection Moulding International* for one year

Your contact details

Title Forename(s) Family Name

Job Title/Position

Organisation

Full address

.....

Postcode..... Country

Tel: Fax:

E-mail:

Subscription period

Powder Injection Moulding International is published on a quarterly basis. The subscription fee is £95.00 for one year (four issues). Your subscription will commence with the next available issue unless otherwise stated below.

Please start subscription with issue:

Multiple subscription discount - save 25%

Organisations wishing to purchase four or more subscriptions to *Powder Injection Moulding International* can receive 25% discount on the total cost. Please contact Paul Whittaker, email: paul@inovar-communications.com, to order.

Payment options

Please invoice me for £95.00. I understand that subscriptions will not start until full payment is made.

Please charge £95.00 to my credit card as follows: VISA MasterCard American Express

Name on Card:.....

Card Number:..... 3/4 Digit Security Code

Expiry Date:.....

Signature:..... Date:.....



Fax to: +44 (0) 1743 469 909

Or mail to: Inovar Communications Ltd
2, The Rural Enterprise Centre, Battlefield Enterprise Park
Shrewsbury SY1 3FE, United Kingdom
Email: paul@inovar-communications.com.
Tel: +44 (0)1743 454 990